


SPECTRUM DATA

OPTIMA HB700

DATE : May,29.1998

Wavelength(nm)	200	210	220	230	240	250	260	270	280	290	300	310	320	330	340
Transmissivity(%)	0.021	0.020	0.021	0.020	0.020	0.018	0.018	0.018	0.018	0.021	0.020	0.021	0.021	0.021	0.021
Wavelength(nm)	350	360	370	380	390	400	410	420	430	440	450	460	470	480	490
Transmissivity(%)	0.023	0.024	0.021	0.021	0.021	0.020	0.020	0.018	0.018	0.018	0.017	0.017	0.017	0.017	0.017
Wavelength(nm)	500	510	520	530	540	550	560	570	580	590	600	610	620	630	640
Transmissivity(%)	0.015	0.015	0.017	0.017	0.015	0.015	0.017	0.018	0.021	0.028	0.035	0.044	0.064	0.090	0.142
Wavelength(nm)	650	660	670	680	690	700	710	720	730	740	750	760	770	780	790
Transmissivity(%)	0.238	0.479	1.349	5.760	22.710	49.600	68.100	77.240	81.880	84.270	85.410	86.070	86.470	86.630	86.880
Wavelength(nm)	800	810	820	830	840	850	860	870	880	890	900				
Transmissivity(%)	87.010	87.110	87.160	87.300	87.330	87.460	87.410	87.540	87.550	87.100	88.200				

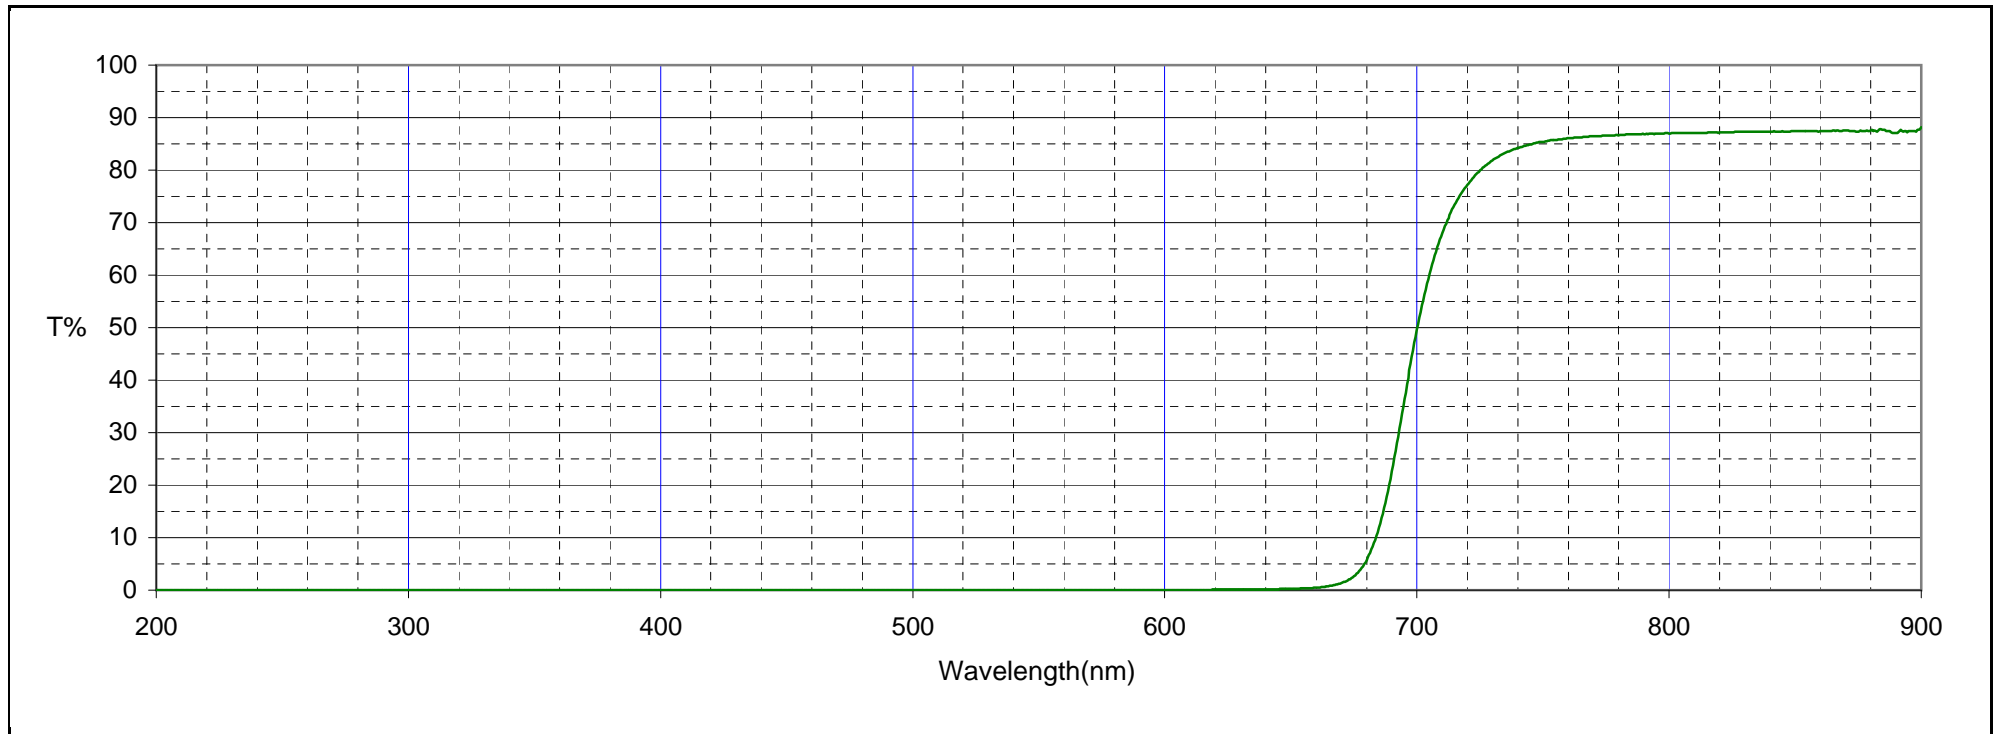

Color Glass Filter (OPTIMA INC. JAPAN)

- 1) Model : OPTIMA HB700 (SCHOTT RG695 Equivalent)
- 2) Melt No.: 011022
- 3) Size : 50mm x 50mm x 2mm t
- 4) Test No.: 9805-009

Inspector : Technomart Inc. Eng. Div.

SEO, IL-SOO