


SPECTRUM DATA

OPTIMA ZB3

DATE : May,29.1988

Wavelength(nm)	200	210	220	230	240	250	260	270	280	290	300	310	320	330	340
Transmissivity(%)	0.029	0.023	0.026	0.024	0.021	0.023	0.024	0.121	2.686	16.040	36.050	54.060	66.410	74.670	79.020
Wavelength(nm)	350	360	370	380	390	400	410	420	430	440	450	460	470	480	490
Transmissivity(%)	81.590	83.050	82.940	80.710	77.570	70.830	61.370	48.730	34.340	20.780	9.842	3.160	0.543	0.072	0.023
Wavelength(nm)	500	510	520	530	540	550	560	570	580	590	600	610	620	630	640
Transmissivity(%)	0.018	0.021	0.018	0.018	0.018	0.018	0.018	0.018	0.020	0.020	0.018	0.018	0.018	0.020	0.018
Wavelength(nm)	650	660	670	680	690	700	710	720	730	740	750	760	770	780	790
Transmissivity(%)	0.018	0.020	0.021	0.021	0.020	0.024	0.310	4.196	18.780	41.620	61.750	75.220	82.230	85.270	86.470
Wavelength(nm)	800	810	820	830	840	850	860	870	880	890	900				
Transmissivity(%)	86.670	86.460	86.100	85.600	84.880	84.260	83.520	82.730	81.700	80.110	79.920				

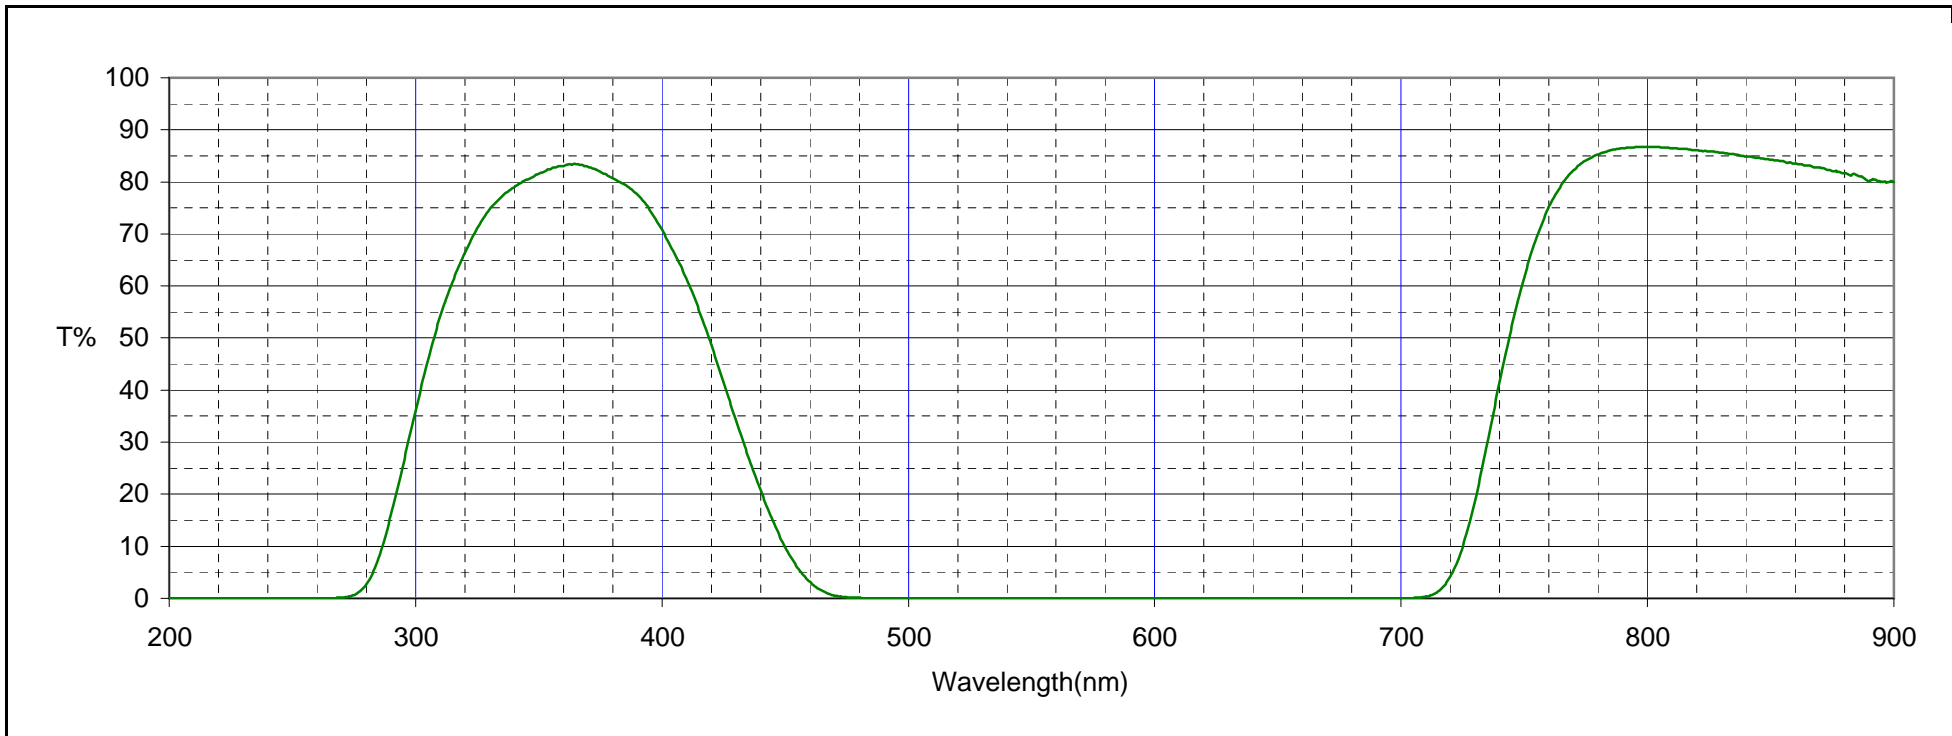

Color Glass Filter (OPTIMA INC. JAPAN)

- 1) Model : OPTIMA ZB3
- 2) Melt No.: 011227
- 3) Size : 50mm x 50mm x 2mm t
- 4) Test No.: 9805-026

Inspector : Technomart Inc. Eng. Div.

SEO, IL-SOO